

# SOIL STABILIZATION WITH FLYASH AND WHEAT HUSK ASH – IMPROVEMENTS IN ENGINEERING CHARACTERISTICS

**Robert M. Brooks\* and Hamza Al-Ayaydah**

Department of Civil and Environmental Engineering

Temple University, Philadelphia 19122

\*Email: [rmbrooks@temple.edu](mailto:rmbrooks@temple.edu); Tel: (215) 204-6348; Fax: (215) 204-4696

## ABSTRACT

Clays are weak and highly compressible by nature. These characteristics play a major role in the stability of any structure constructed over clay soil. The objective of this paper is to stabilize soil with the fly ash and wheat husk ash. For this purpose an expansive clay was mixed with fly ash and wheat husk ash. Several engineering improvements have been tested and discussed as a result of this study. The conclusion includes the following: when the WHA content was increased from 0 to 12%, CBR improved from 1.9 to 7.0 % for 0% flyash. The swelling potential of expansive soil decreases with increasing swell reduction layer thickness ratio.

*Key words:* Construction Materials, Clays, Wheat Husk Ash, Flyash.

## 1. INTRODUCTION

Clay soils cause several problems under various structures. For example, clays cause uneven settlements of walls in houses<sup>1</sup>. Clays have low resilient modulus value and hence are weak and highly compressible by nature<sup>2,3</sup>. These characteristics play a major role in the stability of any structure constructed over clay soil. Many reasons contribute to this uneven settlement. These include but not limited to poorly compacted soil, soils with weak bearing capacity, changes in soil moisture due to natural or artificial conditions, trees and vegetation, and though last but not the least vibrations around the building.

Negligible natural settlement over a long period of time causing uniform deformation is not a serious problem to the super structure. However, a differential settlement results in structural damage to the buildings. Examples of such structural damage include cracks in the walls and slabs. This causes serious devaluation of the real-estate value of the building. Among other problems, the uneven permanent deformations in the walls lead to lopsided alignment of doors and windows. This slanted framework of doors and windows cause them poorly operable. A text book example of uneven settlement is the leaning tower of Pisa. Adding admixtures to such type of soil using fly ash and wheat husk ash would make the necessary improvements in the engineering characteristics indicated by the results in this study.

## 2. MATERIALS

### 2.1. SOILS

As per the USCS classification system, the soil is a CH soil.

### 2.2. FLYASH

Table 1 shows the constituents of Class C flyash used in this study.

### 2.3. WHEAT HUSK ASH

In this investigation, WHA passing through No. 100 sieve (150 micrometers) was used. The chemical composition of WHA is listed in Table 2. The WHA had 56% silica content. This amount provides good pozzolanic action.

### 2.4. EXPERIMENTS

Several simple but valuable tests were conducted to support the efficacy of the paper. These include the following tests: UCS, CBR, compaction and swell-shrinkage tests.

### 2.5. Compaction

The tests were performed in accordance with ASTM D 1557. The specimens were of 102mm diameter and 116mm height.

## 2.6. UCS

The bearing capacity test is a thorough test that simulates more closely the realistic field conditions of the soil. It may not be practical to conduct the full scale bearing capacity test because it is time consuming and costly. However, the unconfined compression test is a low cost test since it makes use of the undisturbed soil. It quantifies the undrained and unconsolidated strength of a cohesive soil in the laboratory.

The UCS tests were performed in accordance with ASTM D 2166. The sample sizes were of 40mm diameter and 80mm length.

## 2.7. CBR

The CBR tests were conducted in accordance with ASTM D 1883. The sample sizes were of 152mm diameter and 126mm length.

## 2.8. Swelling

Consolidation test (ASTM D 2435) setup was used for determining the cyclic swell-shrink behavior of the soil. The sample sizes were 76mm and 50mm in diameter and height respectively. The samples were prepared at Proctor's dry densities. The compacted admixture was cured for 14 days and placed over the expansive soil. The efficacy of WHA as a cushioning layer between the foundation and subgrade was also tested using the consolidation test.

## 3. TEST RESULTS AND DISCUSSION

The following mechanism explains the obtained improvements. The chemical reactions that occur when flyash is mixed with clay include pozzolanic reactions, cation exchange<sup>4</sup>, carbonation and cementation. These result in agglomeration in large size particles. This causes the increase in compressive strength<sup>5</sup>. Influence of flyash content on the UCS of WHA is presented in Figure 1.

The influence of flyash on the stress strain behavior of the clay specimens in UCS test is shown in Fig. 2. The flyash content varied from 0 to 30%. When flyash was increased from 0 % to 25 %, the compressive strength increased from 382 to 618 kPa at a strain of 6%. When flyash was increased from 0 % to 25 %, the compressive strength increased from 303 to 775 kPa at a strain of 9% as shown in Fig. 2.

The influence of WHA on CBR of clay-flyash mix is shown in Fig. 3. At any flyash content, addition of WHA up to 12% led to increases in CBR. Further increase in WHA decreased CBR, indicating that 12% is the optimum value of WHA. When the WHA content was increased from 0 to 12%, CBR improved from 1.9 to 7.0 for 0% flyash. When the WHA content was increased from 0 to 12%, CBR improved from 3.3 to 9.4 % for 25% flyash as shown in Figure 3.

Fig. 4 shows the influence of number of cycles on swell percent. Fig. 5 shows the influence of swell reduction layer thickness ratio on percent swell for various surcharges.

At 15% flyash and 12% WHA, for a 28 day curing period, the UCS is 854 kPa as shown in Figure 1. As per Kate and Katti<sup>6</sup>, this qualifies as a cushioning material at 15% flyash. Similar results were found by Sivapulliah et al.<sup>7</sup> for an WHA-lime mixture.

References 8 through 19 deal with more research studies on the behavior of clays and admixtures of other husk materials. References 20 through 39 indicate the importance of this research study which is applied in class room teachings for the benefit of engineering students.

## 4. CONCLUSIONS

The following are the conclusions.

1. The swelling potential of expansive soil decreases with increasing swell reduction layer thickness ratio.
2. When the WHA content was increased from 0 to 12%, CBR improved from 1.9 to 7.0 % for 0% flyash.

## 5. LIMITATIONS OF THIS STUDY

The results of this paper are limited to the materials tested in this study. More materials need to be tested to increase the scope of this study.

## 6. REFERENCES

- [1]. Liu, C., and Evett, J., "*Soils and Foundations*", 2008, Pearson-Prentice Hall, Seventh Edition, Upper Saddle River, New Jersey.

- [2]. Mitchell, J.K., "Practical Problems from surprising soil Behavior," *J. Geotech. Eng.*, 1986, Vol. 112, No. 3, 255-289.
- [3]. Drumm, E.C., Reeves, J.S., Madgett, M.R., and Trolinger, W.D., "Subgrade Resilient Modulus Correction for Saturated Effects". *Journal of Geotechnical Geo-environmental engineering*, 1997, Vol. 123, No. 7, pp. 663-670.
- [4]. McManis, K.L. and Arman, A. "Class C Flyash as a Full or Partial Replacement for Portland Cement or Lime" *Transportation Research Record*, 1989, Transportation Research Board, National Research Council, Washington, D.C., 1219, 68-81.
- [5]. Misra, A. "Stabilization Characteristics of Clays Using Class C Fly Ash" *Transportation Research Record*, 2000, Transportation Research Board, National Research Council, Washington, D.C, 1611, 46-54.
- [6]. Kate, J.M. and Katti, R.K., "Effect of CNS layer on the behavior of underlying expansive soils media: an experimental study", 1980, *Indian Geotechnical Journal*, 281-305.
- [7]. Sivapulliah P.V., Subba Rao K.S., and Gurumurthy, J.V., "Stabilization of rice husk ash as cushion below foundations on expansive soils", *Ground Improvement*, 2004, Vol. 8, No. 4, pp 137-149.
- [8]. Brooks, R., Udoeyo, F., and Takkalapelli, K. "Geotechnical Properties of Problem Soils Stabilized with Fly Ash and Limestone Dust in Philadelphia." *J. Mater. Civ. Eng.*, American Society of Civil Engineers, 23(5), 711–716, 2011. [http://ascelibrary.org/mto/resource/1/jmcee7/v23/i5/p711\\_s1](http://ascelibrary.org/mto/resource/1/jmcee7/v23/i5/p711_s1)
- [9]. R. M. Brooks (Corresponding author), F. Udoeyo, and K. V. Takkalapelli, "Compaction Delay Characteristics of Clay with Cement Kiln Dust", *UK Institute of Civil Engineers, Geotechnical Engineering Volume 162, issue 5, ISSN: 1353-2618, pp 283-286, Oct 2009.* <http://www.icevirtuallibrary.com/content/article/10.1680/geng.2009.162.5.283>
- [10]. Robert Brooks (Corresponding author), Mozghan Bahadory, Fernando Tovia and Hossein Rostami, "Properties of Alkali Activated Fly Ash: High Performance to Lightweight" , *International Journal of Sustainable Engineering*, Taylor and Francis V3, No.3, 211-218, September 2010, <http://www.tandfonline.com/doi/abs/10.1080/19397038.2010.487162#preview>
- [11]. Khoury, N., Robert Brooks (Corresponding author), Musharraf M. Zaman, Charbel N. Khoury . "Variations of Resilient Modulus of Subgrade Soils with Postcompaction Moisture Contents", *Transportation Research Record: Journal of the Transportation Research Board, Transportation Research Board of the National Academies, issn 0361-1981, Volume 2101 / 2009, page 72-81.* <http://trb.metapress.com/content/j2h2j8841p067802/>
- [12]. Khoury, N., Brooks, R. (Corresponding author), Khoury, C., and Yada, D., "Modeling Resilient Modulus Hysteretic Behavior with Moisture Variation". *Int. J. Geomech, American Society of Civil Engineers ISSN 1943-5622, 2011.* <http://ascelibrary.org/doi/abs/10.1061/%28ASCE%29GM.1943-5622.0000140>
- [13]. Khoury, N., Ph.D., Robert Brooks (Corresponding Author), Ph.D., P.E., ASCE Fellow, Charbel N. Khoury. Environmental influences on the engineering behavior of unsaturated undisturbed subgrade soils: effect of soil suctions on resilient modulus. *International Journal of Geotechnical Engineering, J. Ross Publishing, Inc 1938-6362, Volume 3, Issue 2 / April 2009, page 303-311.* <http://jrosspub.metapress.com/content/p4310j7pt70707k0/>
- [14]. Hossein Rostami, Robert Brooks (Corresponding Author), Fernando Tovia, Mozghan Bahadory. Development of Lightweight Construction Material From Alkali Activated Fly Ash. *The Journal of Solid Waste Technology and Management. Volume 35. Issue 3, August 2009.* <http://solid-waste.org/journal/abstracts-of-published-papers/volume-35-2009/>
- [15]. Brooks, R., Soil Stabilization with Lime and RHA, *International Journal of Applied Engineering, IJAER, Volume 5, Number 7. pp. 1077-1086, 2010.* <http://www.ripublication.com/Volume/ijaerv5n7.htm>
- [16]. Brooks, R. M. Soil Stabilization with RHA and Flyash, *International Journal of Research and Reviews in Applied Sciences V 1, Issue 3, pp.209-217, 2009.* [http://arpapress.com/Volumes/Vol1Issue3/IJRRAS\\_1\\_3\\_01.pdf](http://arpapress.com/Volumes/Vol1Issue3/IJRRAS_1_3_01.pdf)
- [17]. Kingsley Donaldson, Robert M. Brooks (Corresponding author), Felix F. Udoeyo, and Keerthi V. Takkalapelli. Effects of Fly Ash on Engineering Properties of Clays. *International Journal of Applied Engineering Research. Volume 6, Number 1, pp. 43-52, 2011.* <http://www.ripublication.com/Volume/ijaerv6n1.htm>
- [18]. Khoury, N., Robert M Brooks (Corresponding Author), Santhoshini Yadav Boeni, and Damodar Yada "Variation of Resilient Modulus, Strength, and Modulus of Elasticity of Stabilized Soils with Postcompaction Moisture Contents", *Journal of Materials in Civil Engineering, American Society of Civil Engineers, Volume 25, Number 2, ISSN 0899-1561, pp.160-166, February 2013.* [http://ascelibrary.org/doi/abs/10.1061/\(ASCE\)MT.1943-5533.0000574](http://ascelibrary.org/doi/abs/10.1061/(ASCE)MT.1943-5533.0000574)
- [19]. Robert M. Brooks and Mehmet Cetin. "Water Susceptible Properties of Silt Loam Soil in Subgrades in South West Pennsylvania", *International Journal of Modern Engineering Research. Vol.3, Issue 2, ISSN: 2249-6645, S. No: 57, March- April, 2013, pp. 994-948.* [http://www.ijmer.com/papers/Vol3\\_Issue2/CE32944948.pdf](http://www.ijmer.com/papers/Vol3_Issue2/CE32944948.pdf)
- [20]. Robert Brooks, S. Jahanian, A Pedagogical Strategy for Gradual Enhancement of Creative Performance of the Students, *European Journal of Engineering Education Volume 24, No,1 1999.*
- [21]. S. Jahanian, and Robert Brooks (a/k/a James Matthews). Multidisciplinary Project-A tool for Learning the Subject *Journal of American Society of Engineering Education, V 88, No.2, pp153-162, April 1999.*

- [22]. Robert Brooks, Keerthi V. Takkalapelli, Berk Ayranci, Improvement of Graduate Students Performance In Design, Discovery, And Learning, 2009, AC 2009-2524 ,ASEE 2009 Annual Conference. [http://search.asee.org/search/fetch?url=file%3A%2F%2Flocalhost%2F%3A%2Fsearch%2Fconference%2F19%2FAC%25202009Full2524.pdf&index=conference\\_papers&space=129746797203605791716676178&type=application%2Fpdf&charset=](http://search.asee.org/search/fetch?url=file%3A%2F%2Flocalhost%2F%3A%2Fsearch%2Fconference%2F19%2FAC%25202009Full2524.pdf&index=conference_papers&space=129746797203605791716676178&type=application%2Fpdf&charset=)
- [23]. Robert Brooks, Fernando Tovia, Tony Singh, Amithraj Amavasai, Hossein Rostami, Innovative Training Strategy (Its) for Teaching Assistants, AC 2010-264, ASEE 2010 Annual Conference. [http://search.asee.org/search/fetch?url=file%3A%2F%2Flocalhost%2F%3A%2Fsearch%2Fconference%2F32%2FAC%25202010Full264.pdf&index=conference\\_papers&space=129746797203605791716676178&type=application%2Fpdf&charset=](http://search.asee.org/search/fetch?url=file%3A%2F%2Flocalhost%2F%3A%2Fsearch%2Fconference%2F32%2FAC%25202010Full264.pdf&index=conference_papers&space=129746797203605791716676178&type=application%2Fpdf&charset=)
- [24]. Robert Brooks, Fernando Tovia, Keerthi V. Takkalapelli, Amithraj Amavasai, Hossein Rostami, Naji Khoury, Tony Singh, Improving Creativity in A Graduate Course , AC 2010-72 , ASEE 2010 Annual Conference. [http://search.asee.org/search/fetch?url=file%3A%2F%2Flocalhost%2F%3A%2Fsearch%2Fconference%2F32%2FAC%25202010Full72.pdf&index=conference\\_papers&space=129746797203605791716676178&type=application%2Fpdf&charset=](http://search.asee.org/search/fetch?url=file%3A%2F%2Flocalhost%2F%3A%2Fsearch%2Fconference%2F32%2FAC%25202010Full72.pdf&index=conference_papers&space=129746797203605791716676178&type=application%2Fpdf&charset=)
- [25]. Robert Brooks, Mr. Amithraj Amavasai, Rewarding Levels of Knowledge in Graduate Student Exams, AC 2011-143, ASEE 2011 Annual Conference, Ancouer, B. C. Canada, June 26-29 2011. <http://www.asee.org/public/conferences/1/papers/143/view>
- [26]. Robert Brooks, Naji Khoury, Jyosthna Kavaturu, Mr. Amithraj Amavasai Correlation between “Ethical Issues” and “Grade” Performance in a Graduate Class, AC 2011-147 , ASEE 2011 Annual Conference, Ancouer, B. C. Canada, June 26-29 2011. <http://www.asee.org/public/conferences/1/papers/147/view>
- [27]. Robert Brooks, Jyosthna Kavaturu, Mr. Amithraj Amavasai. Engineering and Technology for Non-Engineering and Non-Science Majors, AC 2011-140, ASEE 2011 Annual Conference, Ancouer, B. C. Canada, June 26-29 2011. <http://www.asee.org/public/conferences/1/papers/140/view>
- [28]. Robert Brooks, Jyosthna Kavaturu, Mr. Amithraj Amavasai Development of Best Practices for New Engineering and Math Educators, AC 2011-135, ASEE 2011 Annual Conference, Ancouer, B. C. Canada, June 26-29 2011. <http://nee.asee.org/ConferencePapers/2011/135.pdf>
- [29]. Robert M. Brooks, Jyothsna K. S., Mehmet Cetin. AC 2012-2992: Creativity for Enhancing The Technological Literacy For Non-Science Majors, ASEE 2012 Annual Conference, San Antonio, June 10-13, 2012. <http://www.asee.org/public/conferences/8/papers/2992/view>
- [30]. Robert M. Brooks, Jyothsna K. S., Mehmet Cetin. AC 2012-2979: Critical Thinking: A Pedagogical Instrument For New Engineering And Science Educators. ASEE 2012. Annual Conference, San Antonio, June 10-13, 2012. <http://www.asee.org/public/conferences/8/papers/2979/view>
- [31]. Robert M. Brooks, Jyothsna K. S., Mehmet Cetin. AC 2012-2977: Science for Non-Science Majors. ASEE 2012 Annual Conference, San Antonio, June 10-13, 2012. <http://www.asee.org/public/conferences/8/papers/2977/view>
- [32]. Robert M. Brooks, Mehmet Cetin., and Jyothsna K. S., Application of Peer Reviewed Journal articles for Enhancing Technological Literacy. ASEE 2013 Annual Conference, Atlanta, June 23-26, 2013.
- [33]. Robert M. Brooks, Mehmet Cetin, and Jyothsna K. S., Sustainability Perspectives of Graduate Students on Transportation Systems and Management. ASEE 2013 Annual Conference, Atlanta, June 23-26, 2013.
- [34]. Robert Brooks, etc. Keeping the Civil Engineering Pipeline Filled- Attracting Young Talent ASEE Global Colloquium, Singapore, Oct 2010.
- [35]. Robert Brooks, etc. Intellectual Dexterity and Strategy to Solutions for Multidisciplinary Problems-Tools for Attracting Students to Study Engineering ASEE Global Colloquium, Singapore, Oct 2010.
- [36]. Robert Brooks, etc. A Strategy to Increase Shelf Life of Engineers ASEE Global Colloquium, Singapore, Oct 2010.
- [37]. Robert Brooks, etc. Assessment of ABET Deliverables in a Senior Design Project Course for Effective Engagement of Our Future Engineers, ASEE Global Colloquium 2009.
- [38]. Robert Brooks, etc. Case Studies - A Tool for Learning Environmental Science Course, ASEE Global Colloquium 2009.
- [39]. Robert Brooks, etc. Post-test- A Tool for an Effective Engagement of Our Future Engineers, ASEE Global Colloquium 2009.

Table 1 Constituents of Fly Ash.

Constituents	%
$\text{SiO}_2$	56.0
$\text{Al}_2\text{O}_3$	21.0
$\text{Fe}_2\text{O}_3$	6.5
CaO	12.2
MgO	3.6
Alkali	1.1
$\text{SO}_3$	1.6
Heavy Metals	trace

Table 2 Chemical Composition of Wheat Husk Ash

Constituent	%
Silica – $\text{SiO}_2$	56
Alumina – $\text{Al}_2\text{O}_3$	21
Calcium Oxide – CaO	12.2
Magnesium Oxide – MgO	0.5
Ferric Oxide – $\text{Fe}_2\text{O}_3$	6.5

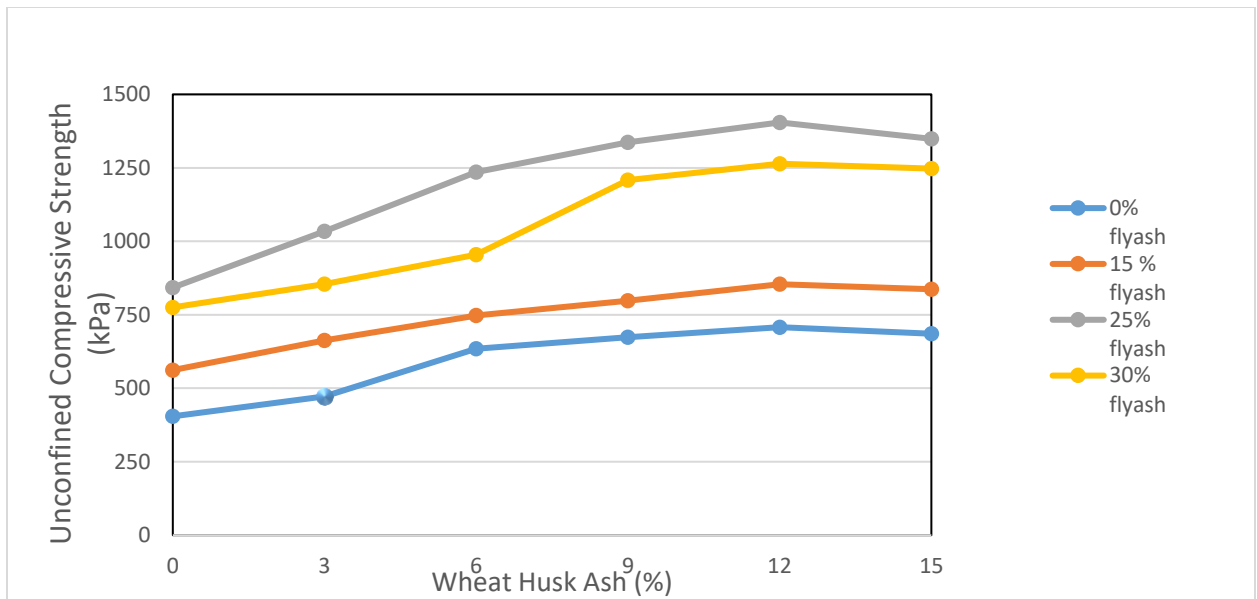


Fig. 1. Influence of WHA on UCS for clay-flyash mixture.

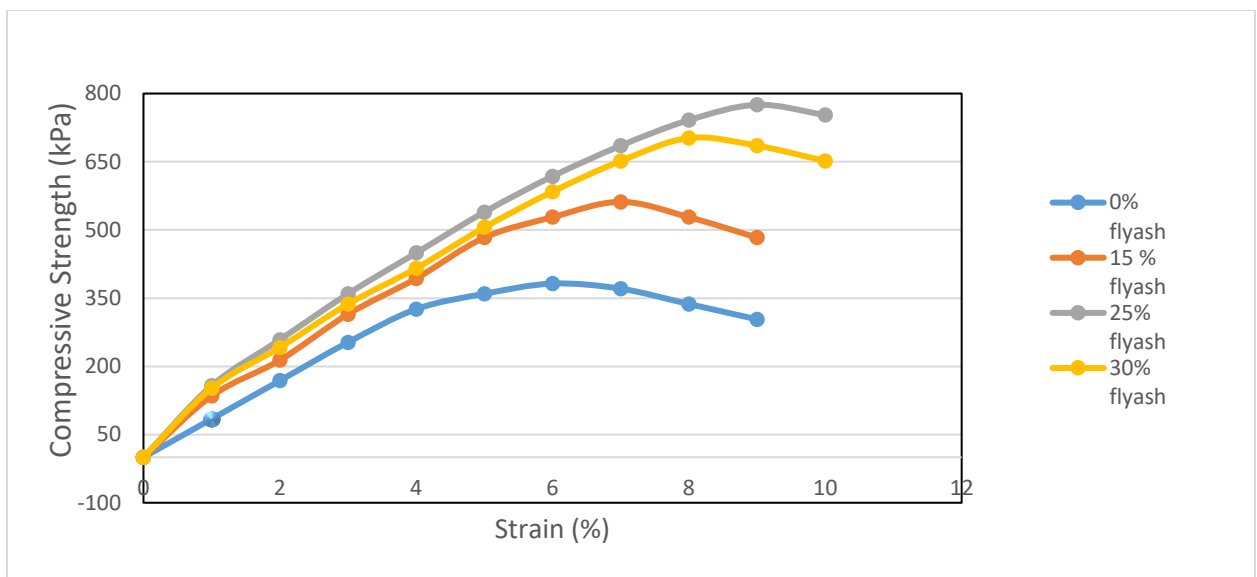


Fig. 2. Influence of flyash on the stress-strain behavior of the soil.

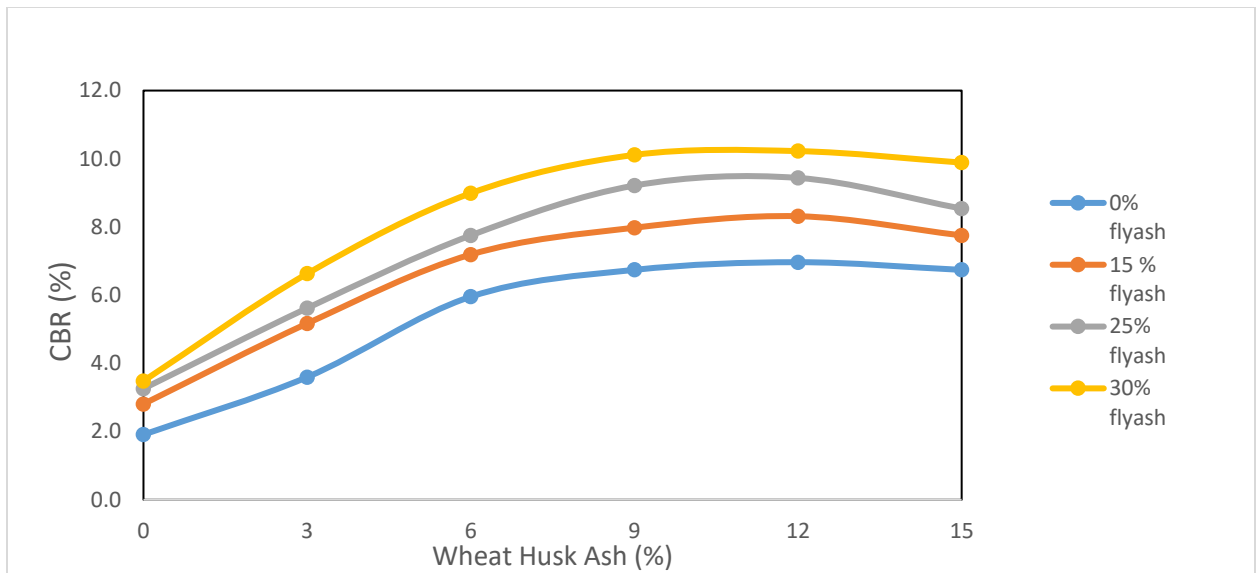


Fig. 3. Influence of WHA on CBR for clay-flyash mixture.

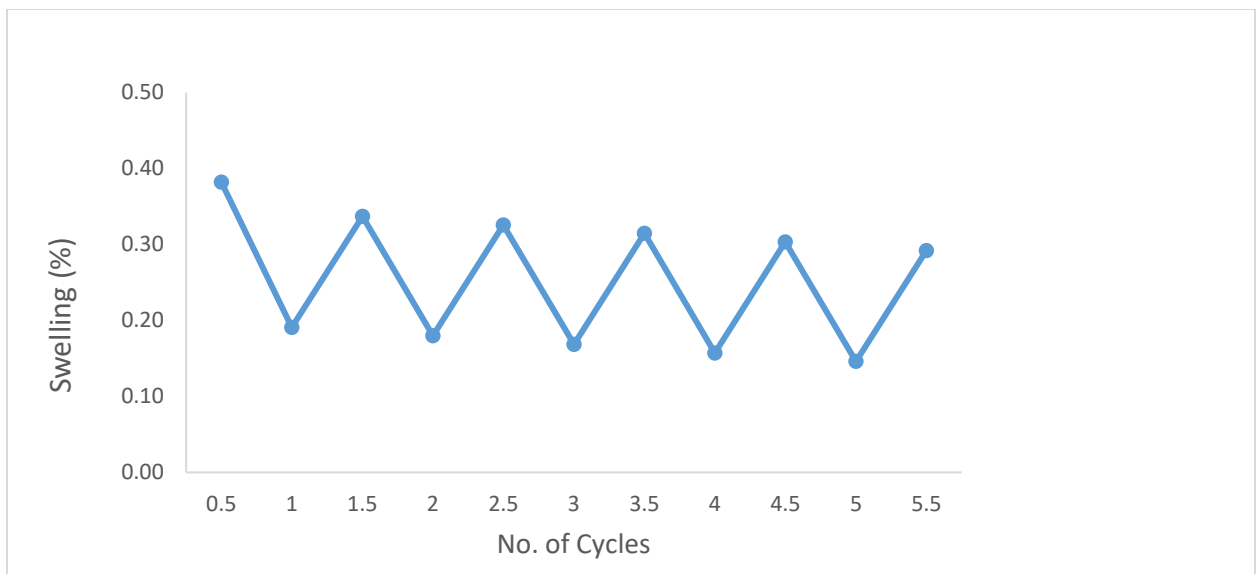


Fig. 4. Influence of number of cycles on swelling of 15% flyash and WHA blend under surcharge of 5kPa.

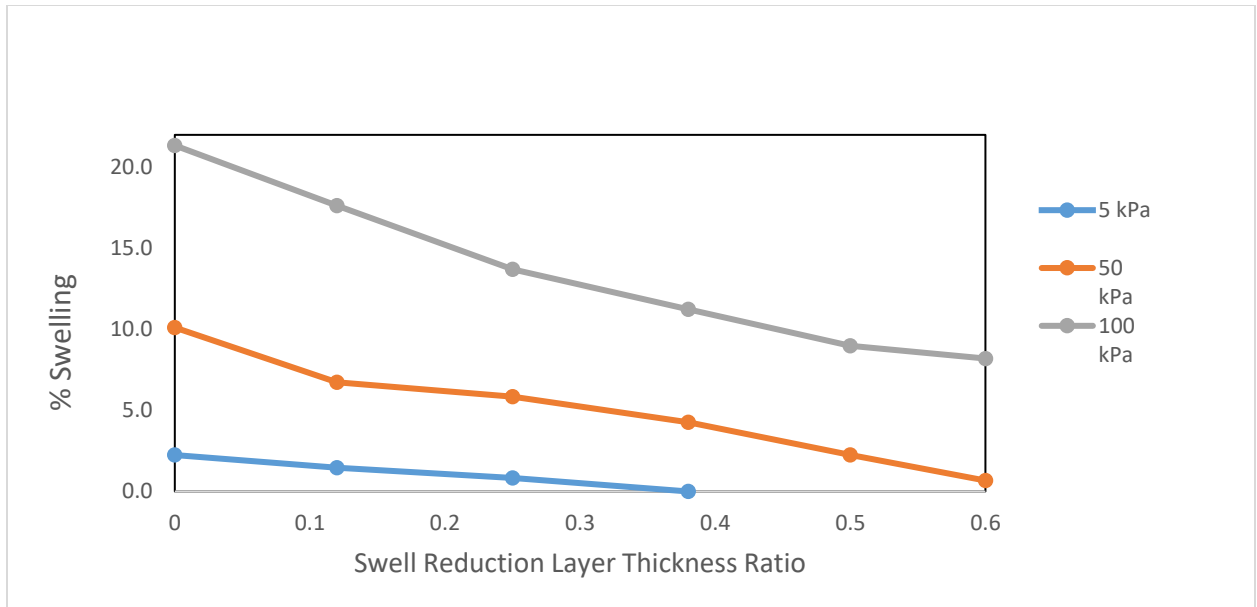


Fig. 5. Influence of Swell reduction layer thickness ratio on swell percentage of soil for various surcharges.